


A16_04_PRECRUSH

Company:
 User:
 Result file: C:\CamsizerXT\CAMDATA\A16_04_PRECRUSH\A16_04_PRECRUSH323.rdf
 Task file: C:\CamsizerXT\CAMSYS\A16_04_PRECRUSH.afg
 Time: 7/16/2015 , 13:02 , duration 16 min 12 s at 0.5 % covered area, image rate 1:1 , with X-Fall, gap width = 7.0 mm

Particle model: xc_min
 No. of particles: CCD-B = 14796611 , CCD-Z = 201375
 Velocity adaption: no
 Fitting: no

Material:

ASTM(+)	No(-)	retained [%]	passing [%]	SPHT3	Symm3	b/l3	PDN
> #16		6.1	100.0	0.777	0.902	0.771	273
#20	#16	3.9	93.9	0.776	0.892	0.734	507
#30	#20	4.5	90.0	0.791	0.883	0.739	1659
#40	#30	5.2	85.5	0.803	0.876	0.746	5430
#50	#40	6.0	80.3	0.827	0.872	0.742	18093
#60	#50	4.4	74.3	0.849	0.871	0.742	28030
#70	#60	5.8	69.9	0.878	0.881	0.747	63228
#140	#70	45.1	64.1	0.898	0.900	0.741	2152127
PAN	#140	19.0	19.0	0.882	0.923	0.717	34554224

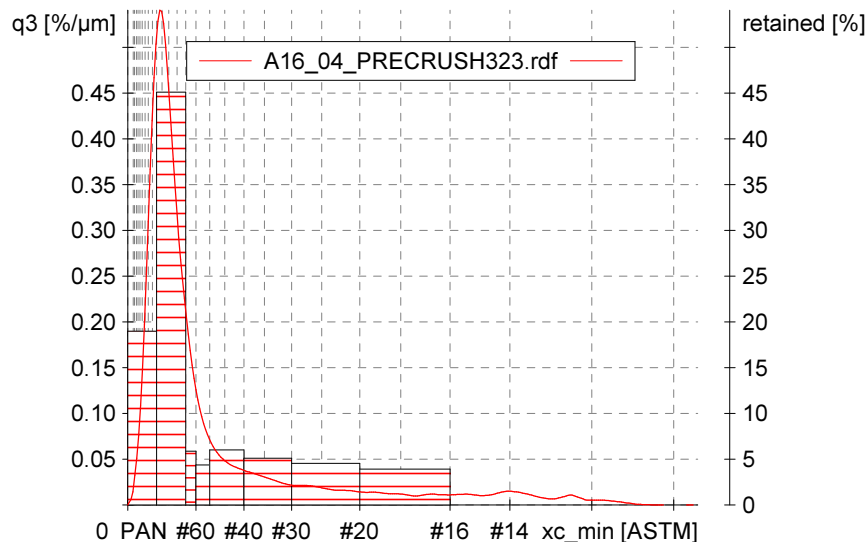

Characteristics

Q3 [%] x [μm]
 10.0 90.0
 50.0 163.6
 90.0 849.4
 SPAN3 = 4.642
 U3 = 2.163
 Mv3(x) = 315.9 μm
 Sigma3(x) = 364.5 μm

Mean value SPHT3 = 0.861
 Mean value Symm3 = 0.897
 Mean value b/l3 = 0.725
 Mean value RDNS_C3 = 0.500
 Mean value SPHT_K3 = 0.656

User