


A16_05_5K

Company:
 User:
 Result file: C:\CamsizerXT\CAMDAT\A16_05_5K\A16_05_5K093.rdf
 Task file: C:\CamsizerXT\CAMSYS\A16_05_5K.afg
 Time: 7/24/2015, 15:27, duration 29 min 49 s at 0.5 % covered area, image rate 1:1, with X-Fall, gap width = 7.0 mm

Particle model: xc_min
 No. of particles: CCD-B = 47542866, CCD-Z = 4930
 Velocity adaption: no
 Fitting: no

Material:

ASTM(+)	No(-)	retained [%]	passing [%]	SPHT3	Symm3	b/l3	PDN
> #16		0.0	100.0				0
#20	#16	0.0	100.0				0
#30	#20	0.0	100.0				0
#40	#30	0.0	100.0				0
#50	#40	0.0	100.0	0.697	0.785	0.746	11
#60	#50	0.1	100.0	0.865	0.870	0.780	922
#70	#60	1.6	99.9	0.899	0.889	0.778	16343
#140	#70	72.8	98.3	0.895	0.901	0.754	3639440
PAN	#140	25.5	25.5	0.817	0.894	0.668	25156506

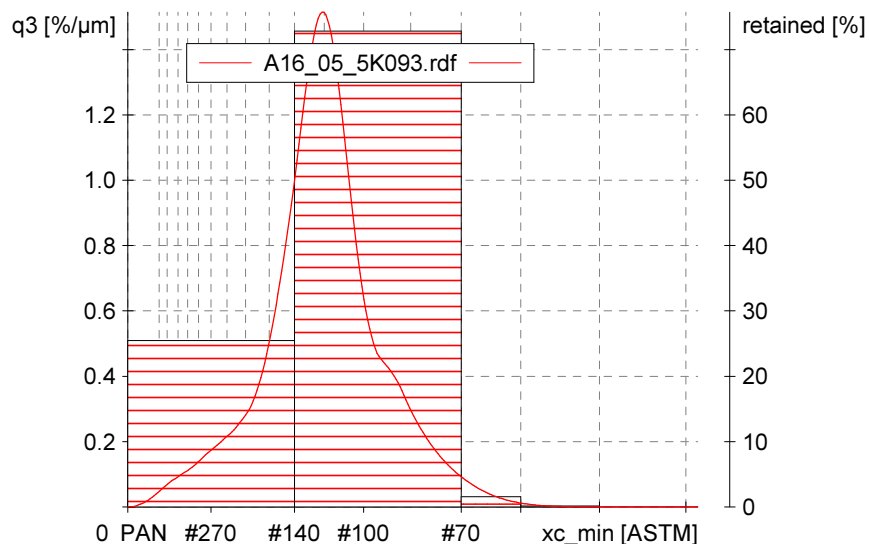

Characteristics

Q3 [%]	x [μm]
10.0	79.7
50.0	124.2
90.0	171.8
SPAN3 =	0.742
U3 =	1.636
Mv3(x) =	124.7 μm
Sigma3(x) =	36.9 μm

Mean value SPHT3 = 0.871
 Mean value Symm3 = 0.898
 Mean value b/l3 = 0.725
 Mean value RDNS_C3 = 0.402
 Mean value SPHT_K3 = 0.658

User