


A23_02_PRECRUSH

Company:
 User:
 Result file: C:\CamsizerXT\CAMDAT\A23_02_PRECRUSH\A23_02_PRECRUSH257.rdf
 Task file: C:\CamsizerXT\CAMSYS\A23_02_PRECRUSH.afg
 Time: 7/14/2015, 10:50, duration 11 min 37 s at 0.5 % covered area, image rate 1:1, with X-Fall, gap width = 7.0 mm

Particle model: xc_min
 No. of particles: CCD-B = 11037465, CCD-Z = 176517
 Velocity adaption: no
 Fitting: no

Material:

ASTM(+)	No(-)	retained [%]	passing [%]	SPHT3	Symm3	b/l3	PDN
> #16		0.0	100.0				0
#20	#16	0.1	100.0	0.798	0.891	0.719	11
#30	#20	0.1	99.9	0.799	0.884	0.710	64
#40	#30	1.1	99.8	0.813	0.873	0.762	1690
#50	#40	5.6	98.7	0.832	0.867	0.751	21375
#60	#50	6.1	93.1	0.849	0.864	0.744	46866
#70	#60	7.8	87.0	0.872	0.872	0.738	95603
#140	#70	72.9	79.2	0.909	0.909	0.739	3316774
PAN	#140	6.3	6.3	0.892	0.931	0.710	26245449

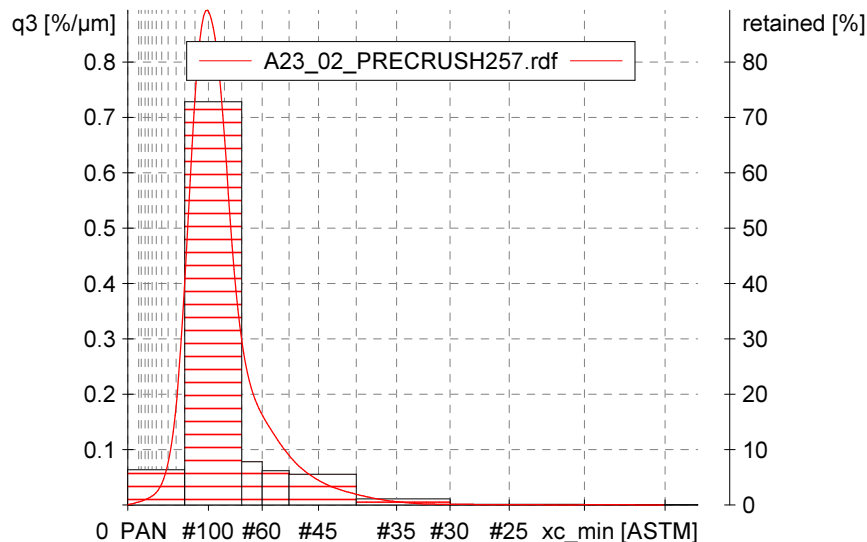

Characteristics

Q3 [%]	x [μm]
10.0	114.1
50.0	161.6
90.0	271.0
SPAN3 = 0.971	
U3 = 1.513	
Mv3(x) = 178.8 μm	
Sigma3(x) = 74.2 μm	

Mean value SPHT3 = 0.889
 Mean value Symm3 = 0.900
 Mean value b/l3 = 0.723
 Mean value RDNS_C3 = 0.609
 Mean value SPHT_K3 = 0.646

User