


A29_02_PRECRUSH

Company:
 User:
 Result file: C:\CamsizerXT\CAMDATA\A29_02_PRECRUSH\A29_02_PRECRUSH290.rdf
 Task file: C:\CamsizerXT\CAMSYS\A29_02_PRECRUSH.afg
 Time: 7/15/2015, 13:06, duration 12 min 14 s at 0.5 % covered area, image rate 1:1, with X-Fall, gap width = 7.0 mm

Particle model: xc_min
 No. of particles: CCD-B = 20824435, CCD-Z = 192045
 Velocity adaption: no
 Fitting: no

Material:

ASTM(+)	No(-)	retained [%]	passing [%]	SPHT3	Symm3	b/l3	PDN
> #16		0.2	100.0	0.829	0.887	0.803	14
#20	#16	0.8	99.8	0.798	0.877	0.751	128
#30	#20	1.6	99.0	0.817	0.884	0.741	755
#40	#30	3.3	97.4	0.832	0.871	0.750	4656
#50	#40	13.7	94.1	0.881	0.885	0.756	56192
#60	#50	19.1	80.4	0.906	0.899	0.752	151073
#70	#60	20.5	61.3	0.914	0.905	0.741	255693
#140	#70	38.8	40.8	0.907	0.907	0.726	1377065
PAN	#140	2.0	2.0	0.852	0.907	0.685	37660903

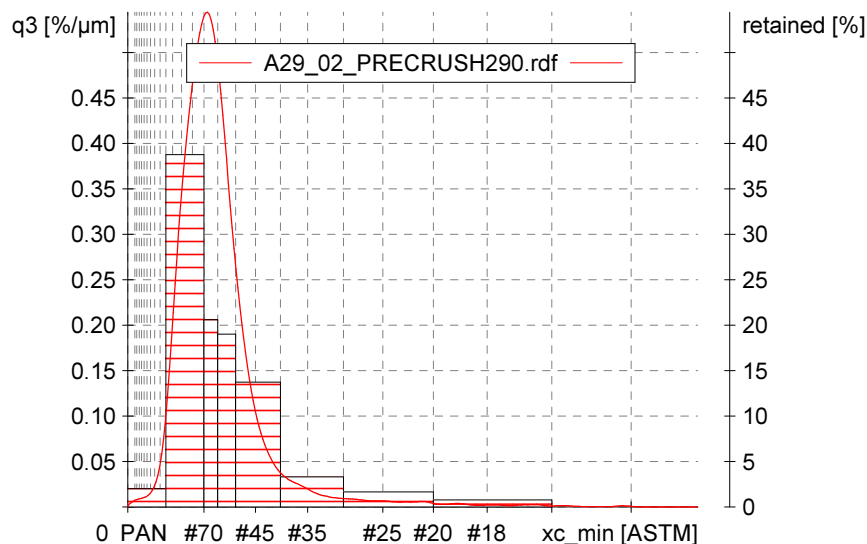

Characteristics

Q3 [%]	x [μm]
10.0	144.3
50.0	228.6
90.0	357.0
SPAN3 =	0.931
U3 =	1.714
Mv3(x) =	251.8 μm
Sigma3(x) =	130.0 μm

Mean value SPHT3 = 0.893
 Mean value Symm3 = 0.899
 Mean value b/l3 = 0.724
 Mean value RDNS_C3 = 0.535
 Mean value SPHT_K3 = 0.651

User