


A38_02_5K

Company:
 User:
 Result file: C:\CamsizerXT\CAMDAT\A38_02_5K\A38_02_5K088.rdf
 Task file: C:\CamsizerXT\CAMSYS\A38_02_5K.afg
 Time: 7/23/2015, 12:14, duration 30 min 49 s at 0.5 % covered area, image rate 1:1, with X-Fall, gap width = 7.0 mm

Particle model: xc_min
 No. of particles: CCD-B = 40590730, CCD-Z = 33472
 Velocity adaption: no
 Fitting: no

Material:

ASTM(+)	No(-)	retained [%]	passing [%]	SPHT3	Symm3	b/l3	PDN
> #16		0.0	100.0				0
#20	#16	0.0	100.0	0.463	0.823	0.607	4
#30	#20	0.1	100.0	0.528	0.801	0.619	14
#40	#30	0.1	99.9	0.680	0.813	0.683	102
#50	#40	0.5	99.8	0.760	0.817	0.718	1405
#60	#50	2.3	99.3	0.857	0.863	0.751	12794
#70	#60	13.3	97.0	0.911	0.898	0.763	119206
#140	#70	74.4	83.7	0.904	0.903	0.735	2104792
PAN	#140	9.3	9.3	0.818	0.887	0.664	29512705

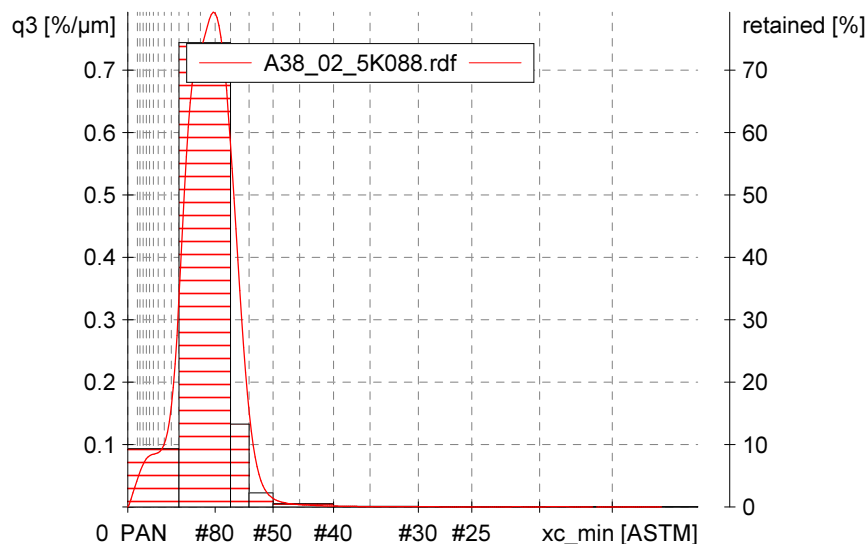

Characteristics

Q3 [%]	x [μm]
10.0	108.0
50.0	167.7
90.0	224.0
SPAN3 =	0.692
U3 =	1.667
Mv3(x) =	166.0 μm
Sigma3(x) =	54.4 μm

Mean value SPHT3 = 0.889
 Mean value Symm3 = 0.898
 Mean value b/l3 = 0.719
 Mean value RDNS_C3 = 0.398
 Mean value SPHT_K3 = 0.638

User