


A38_02_PRECRUSH

Company:
 User:
 Result file: C:\CamsizerXT\CAMDATA\A38_02_PRECRUSH\A38_02_PRECRUSH192.rdf
 Task file: C:\CamsizerXT\CAMSYS\A38_02_PRECRUSH.afg
 Time: 7/7/2015 , 11:03 , duration 9 min 9 s at 0.5 % covered area, image rate 1:1 , with X-Fall, gap width = 7.0 mm

Particle model: xc_min
 No. of particles: CCD-B = 5296439 , CCD-Z = 53172
 Velocity adaption: no
 Fitting: no

Material:

ASTM(+)	No(-)	retained [%]	passing [%]	SPHT3	Symm3	b/l3	PDN
> #16		0.1	100.0	0.776	0.866	0.769	9
#20	#16	0.8	99.9	0.811	0.878	0.715	149
#30	#20	2.1	99.1	0.834	0.883	0.722	1013
#40	#30	5.8	97.0	0.874	0.892	0.744	8431
#50	#40	18.5	91.2	0.897	0.898	0.747	74398
#60	#50	16.0	72.7	0.905	0.901	0.740	130882
#70	#60	15.4	56.7	0.910	0.903	0.734	202593
#140	#70	37.0	41.3	0.902	0.907	0.723	1609700
PAN	#140	4.3	4.3	0.867	0.926	0.703	14570374

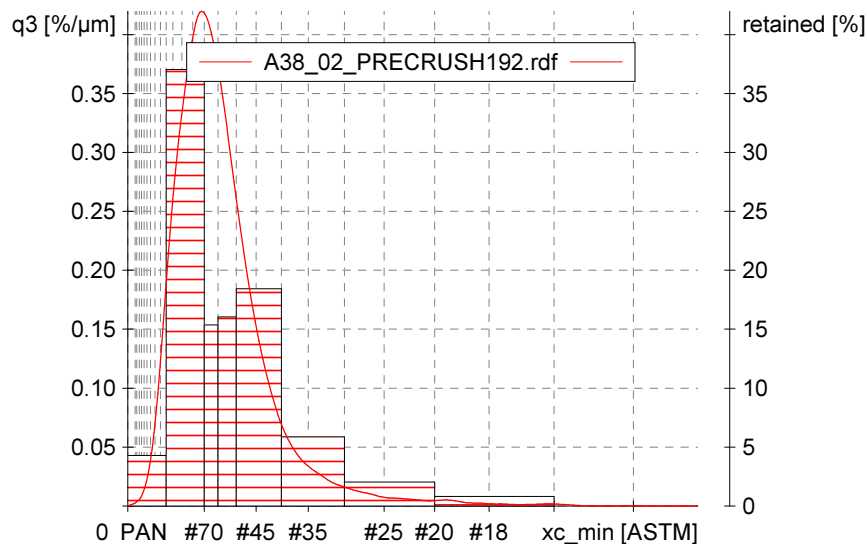

Characteristics

Q3 [%] x [μm]
 10.0 128.6
 50.0 232.7
 90.0 409.3
 SPAN3 = 1.206
 U3 = 2.013
 Mv3(x) = 260.8 μm
 Sigma3(x) = 139.2 μm

Mean value SPHT3 = 0.890
 Mean value Symm3 = 0.901
 Mean value b/l3 = 0.715
 Mean value RDNS_C3 = 0.624
 Mean value SPHT_K3 = 0.625

User