


A7-2_Crush6k

Company:
 User:
 Result file: C:\CamsizerXT\CAMDAT\A7-2_Crush6k\A7-2_Crush6k011.rdf
 Task file: C:\CamsizerXT\CAMSYS\A7-2_Crush6k.afg
 Time: 11/13/2014, 11:06, duration 27 min 22 s at 0.5 % covered area, image rate 1:1, with X-Fall, gap width = 7.0 mm

Particle model: xc_min
 No. of particles: CCD-B = 62163643, CCD-Z = 824376
 Velocity adaption: no
 Fitting: no

Material:

ASTM(+)	No(-)	retained [%]	passing [%]	SPHT3	Symm3	b/l3	PDN
> #16		0.0	100.0				0
#20	#16	0.0	100.0				0
#30	#20	0.0	100.0	0.534	0.806	0.750	1
#40	#30	0.0	100.0	0.770	0.889	0.692	4
#50	#40	0.0	100.0	0.717	0.788	0.731	274
#60	#50	0.6	100.0	0.859	0.864	0.774	7748
#70	#60	6.3	99.4	0.912	0.898	0.781	139886
#140	#70	73.5	93.1	0.910	0.906	0.751	6161566
PAN	#140	19.6	19.6	0.889	0.922	0.720	194034307

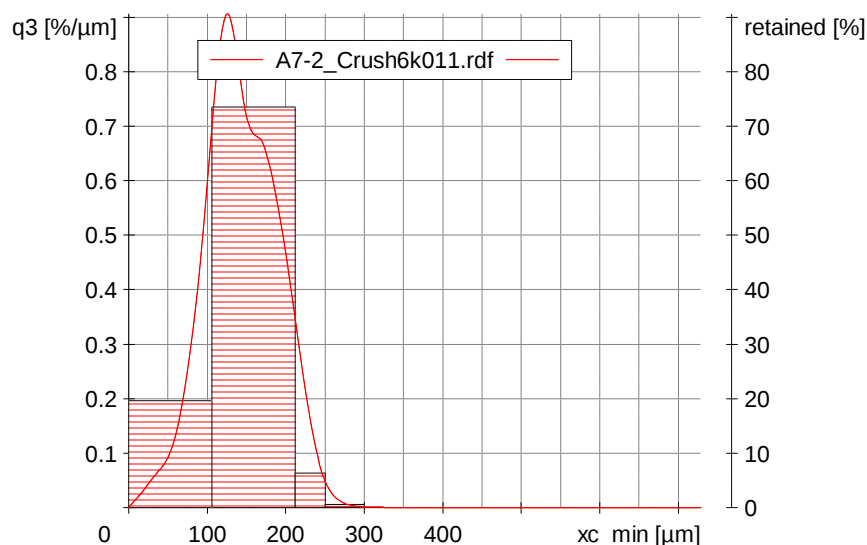

Characteristics

Q3 [%]	x [μm]
10.0	88.2
50.0	140.5
90.0	203.9
SPAN3 =	0.823
U3 =	1.752
Mv3(x) =	143.7 μm
Sigma3(x) =	45.4 μm

Mean value SPHT3 = 0.900
 Mean value Symm3 = 0.907
 Mean value b/l3 = 0.731
 Mean value RDNS_C3 = 0.656
 Mean value SPHT_K3 = 0.662

User