


B59_01_5KCRUSH

Company:
 User:
 Result file: C:\CamsizerXT\CAMDAT\B59_01_5KCRUSH\B59_01_5KCRUSH132.rdf
 Task file: C:\CamsizerXT\CAMSYS\B59_01_5KCRUSH.afg
 Time: 10/21/2015 , 11:32 , duration 29 min 33 s at 0.5 % covered area, image rate 1:1 , with X-Fall, gap width = 7.0 mm

Particle model: xc_min
 No. of particles: CCD-B = 44560017 , CCD-Z = 532674
 Velocity adaption: no
 Fitting: no

Material:

ASTM(+)	No(-)	retained [%]	passing [%]	SPHT3	Symm3	b/l3	PDN
> #16		0.0	100.0				0
#20	#16	0.0	100.0				0
#30	#20	0.0	100.0				0
#40	#30	0.0	100.0				0
#50	#40	0.0	100.0	0.675	0.756	0.714	158
#60	#50	0.9	100.0	0.861	0.866	0.772	6793
#70	#60	8.8	99.1	0.910	0.897	0.775	110241
#140	#70	70.1	90.3	0.911	0.906	0.747	3189776
PAN	#140	20.2	20.2	0.891	0.922	0.721	90316279

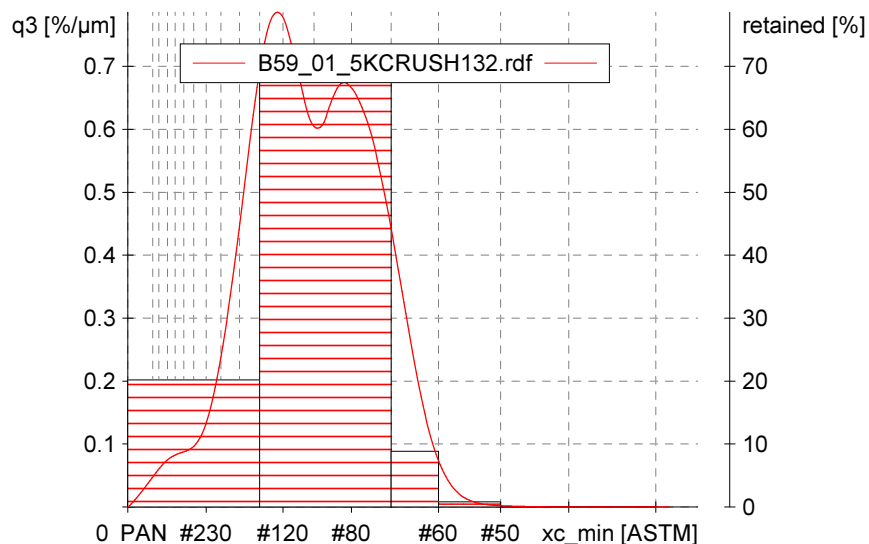

Characteristics

Q3 [%]	x [μm]
10.0	87.7
50.0	146.1
90.0	211.4
SPAN3 = 0.847	
U3 = 1.860	
Mv3(x) = 147.6 μm	
Sigma3(x) = 48.8 μm	

Mean value SPHT3 = 0.900
 Mean value Symm3 = 0.907
 Mean value b/l3 = 0.729
 Mean value RDNS_C3 = 0.663
 Mean value SPHT_K3 = 0.657

User