


B62_01_PRECRUSH

Company:
 User:
 Result file: C:\CamsizerXT\CAMDAT\B62_01_PRECRUSH\B62_01_PRECRUSH162.rdf
 Task file: C:\CamsizerXT\CAMSYS\B62_01_PRECRUSH.afg
 Time: 12/21/2015 , 16:28 , duration 6 min 55 s at 0.5 % covered area, image rate 1:1 , with X-Fall, gap width = 7.0 mm

Particle model: xc_min
 No. of particles: CCD-B = 12391270 , CCD-Z = 187015
 Velocity adaption: no
 Fitting: no

Material:

ASTM(+)	No(-)	retained [%]	passing [%]	SPHT3	Symm3	b/l3	PDN
> #16		1.4	100.0	0.718	0.867	0.759	113
#20	#16	2.4	98.6	0.736	0.865	0.741	519
#30	#20	3.9	96.2	0.759	0.851	0.733	2256
#40	#30	4.8	92.3	0.807	0.849	0.729	7871
#50	#40	34.3	87.5	0.914	0.903	0.767	176884
#60	#50	29.9	53.2	0.917	0.910	0.735	273797
#70	#60	13.7	23.3	0.910	0.910	0.706	192070
#140	#70	9.0	9.6	0.899	0.907	0.695	330069
PAN	#140	0.6	0.6	0.865	0.916	0.699	25880742

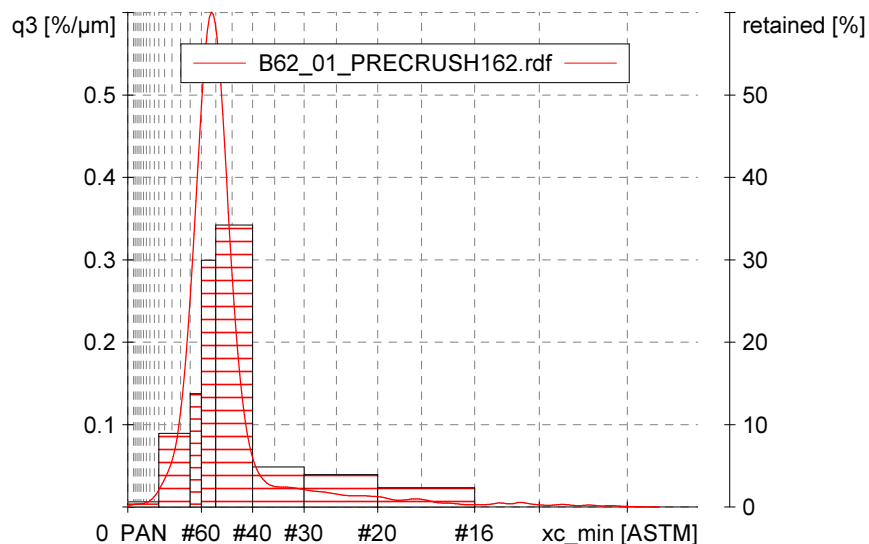

Characteristics

Q3 [%]	x [μm]
10.0	213.7
50.0	294.8
90.0	501.6
SPAN3 = 0.977	
U3 = 1.458	
Mv3(x) = 342.3 μm	
Sigma3(x) = 197.0 μm	

Mean value SPHT3 = 0.889
 Mean value Symm3 = 0.899
 Mean value b/l3 = 0.724
 Mean value RDNS_C3 = 0.615
 Mean value SPHT_K3 = 0.653

User