


B64_02_PRECRUSH

Company:
 User:
 Result file: C:\CamsizerXT\CAMDAT\B64_02_PRECRUSH\B64_02_PRECRUSH051.rdf
 Task file: C:\CamsizerXT\CAMSYS\B64_02_PRECRUSH.afg
 Time: 6/19/2015 , 13:45 , duration 11 min 20 s at 0.5 % covered area, image rate 1:1 , with X-Fall, gap width = 7.0 mm

Particle model: xc_min
 No. of particles: CCD-B = 35088882 , CCD-Z = 319016
 Velocity adaption: no
 Fitting: no

Material:

ASTM(+)	No(-)	retained [%]	passing [%]	SPHT3	Symm3	b/l3	PDN
> #16		12.9	100.0	0.758	0.880	0.735	1143
#20	#16	15.4	87.1	0.767	0.878	0.715	3513
#30	#20	14.9	71.7	0.788	0.877	0.721	9511
#40	#30	14.2	56.8	0.818	0.879	0.729	25856
#50	#40	10.0	42.6	0.844	0.879	0.730	49151
#60	#50	3.4	32.6	0.863	0.881	0.725	37231
#70	#60	3.8	29.2	0.896	0.893	0.753	74956
#140	#70	22.2	25.4	0.913	0.907	0.742	1281679
PAN	#140	3.2	3.2	0.891	0.916	0.748	57598847

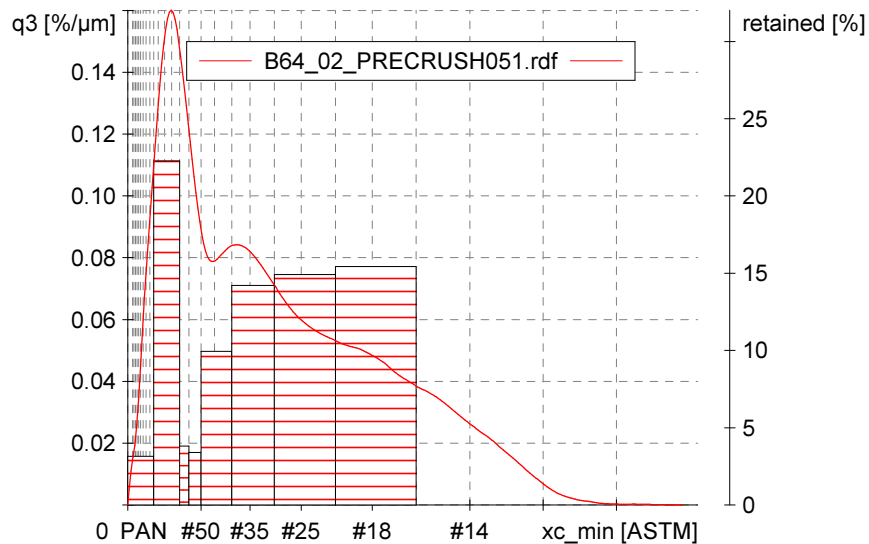

Characteristics

Q3 [%]	x [μm]
10.0	151.8
50.0	510.4
90.0	1257.7
SPAN3 =	2.166
U3 =	4.255
Mv3(x) =	608.3 μm
Sigma3(x) =	427.1 μm

Mean value SPHT3 = 0.824
 Mean value Symm3 = 0.886
 Mean value b/l3 = 0.719
 Mean value RDNS_C3 = 0.336
 Mean value SPHT_K3 = 0.657

User