


B65_05_CRUSH5K

Company:
 User:
 Result file: C:\CamsizerXT\CAMDAT\B65_05_CRUSH5K\B65_05_CRUSH5K041.rdf
 Task file: C:\CamsizerXT\CAMSYS\B65_05_CRUSH5K.afg
 Time: 6/17/2015 , 16:38 , duration 24 min 4 s at 0.5 % covered area, image rate 1:1 , with X-Fall, gap width = 7.0 mm

Particle model: xc_min
 No. of particles: CCD-B = 80634069 , CCD-Z = 627446
 Velocity adaption: no
 Fitting: no

Material:

ASTM(+)	No(-)	retained [%]	passing [%]	SPHT3	Symm3	b/l3	PDN
> #16		0.0	100.0				0
#20	#16	0.0	100.0				0
#30	#20	0.0	100.0	0.783	0.860	0.751	6
#40	#30	0.1	100.0	0.728	0.806	0.733	428
#50	#40	2.1	99.9	0.844	0.854	0.746	24077
#60	#50	31.6	97.8	0.927	0.913	0.785	703558
#70	#60	45.1	66.2	0.932	0.919	0.761	1388064
#140	#70	17.7	21.1	0.908	0.910	0.710	1191357
PAN	#140	3.4	3.4	0.851	0.904	0.695	115685171

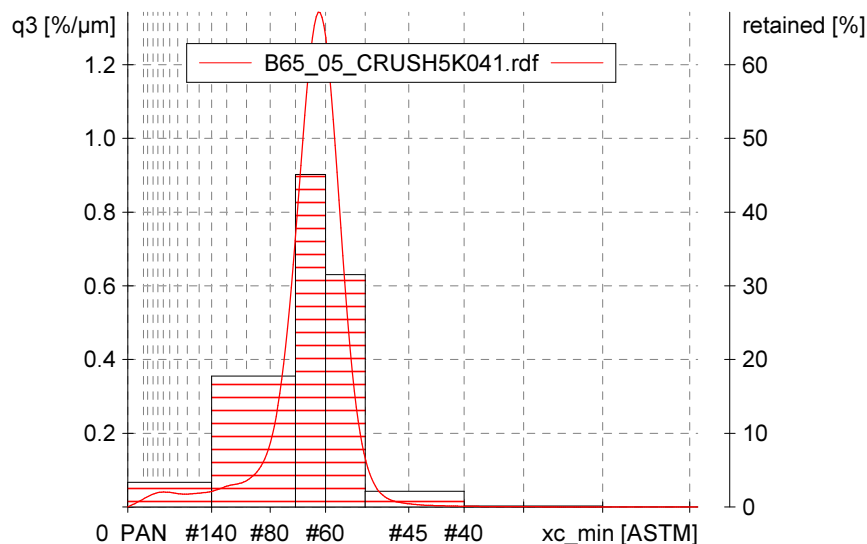

Characteristics

Q3 [%]	x [μm]
10.0	185.8
50.0	238.3
90.0	274.1
SPAN3 = 0.370	
U3 = 1.320	
Mv3(x) = 231.2 μm	
Sigma3(x) = 47.7 μm	

Mean value SPHT3 = 0.916
 Mean value Symm3 = 0.912
 Mean value b/l3 = 0.745
 Mean value RDNS_C3 = 0.579
 Mean value SPHT_K3 = 0.698

User