


B66_01_CRUSH7K

Company:
 User:
 Result file: C:\CamsizerXT\CAMDAT\B66_01_CRUSH7K\B66_01_CRUSH7K057.rdf
 Task file: C:\CamsizerXT\CAMSYS\B66_01_CRUSH7K.afg
 Time: 6/23/2015 , 12:52 , duration 23 min 2 s at 0.5 % covered area, image rate 1:1 , with X-Fall, gap width = 7.0 mm

Particle model: xc_min
 No. of particles: CCD-B = 88633066 , CCD-Z = 917817
 Velocity adaption: no
 Fitting: no

Material:

ASTM(+)	No(-)	retained [%]	passing [%]	SPHT3	Symm3	b/l3	PDN
> #16		0.0	100.0				0
#20	#16	0.0	100.0				0
#30	#20	0.0	100.0	0.753	0.868	0.645	7
#40	#30	0.1	100.0	0.736	0.788	0.731	271
#50	#40	17.4	99.9	0.911	0.901	0.779	138998
#60	#50	38.9	82.5	0.917	0.909	0.752	492630
#70	#60	22.3	43.6	0.912	0.909	0.724	417726
#140	#70	14.9	21.3	0.889	0.899	0.698	833245
PAN	#140	6.4	6.4	0.848	0.898	0.683	147356487

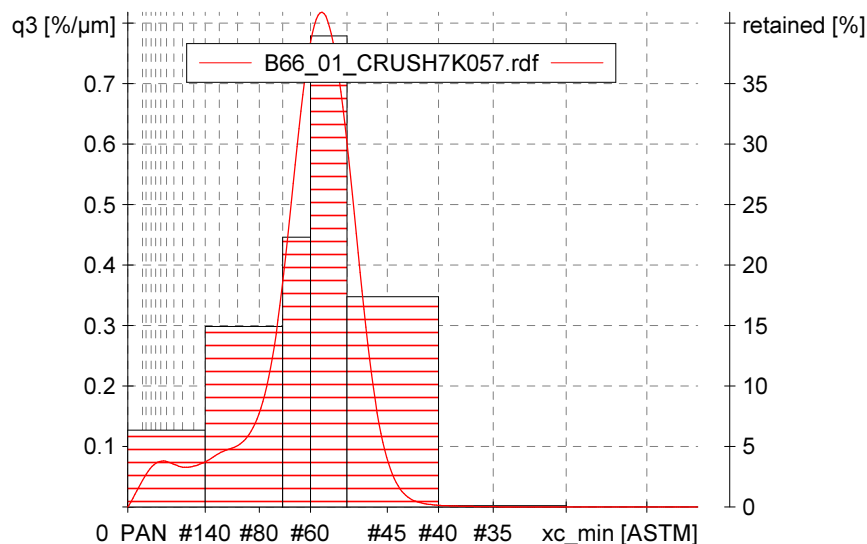

Characteristics

Q3 [%]	x [μm]
10.0	147.1
50.0	257.9
90.0	314.3
SPAN3 = 0.648	
U3 = 1.834	
Mv3(x) = 244.8 μm	
Sigma3(x) = 69.1 μm	

Mean value SPHT3 = 0.901
 Mean value Symm3 = 0.904
 Mean value b/l3 = 0.724
 Mean value RDNS_C3 = 0.627
 Mean value SPHT_K3 = 0.645

User