


BELT_08_SV_14_PRECRUSH

Company:
 User:
 Result file: C:\CamsizerXT\CAMDAT\BELT_08_SV_14_PRECRUSH\BELT_08_SV_14_PRECRUSH106.rdf
 Task file: C:\CamsizerXT\CAMSYS\BELT_08_SV_14_PRECRUSH.afg
 Time: 6/8/2015, 14:06, duration 12 min 7 s at 0.5 % covered area, image rate 1:1, with X-Fall, gap width = 7.0 mm

Particle model: xc_min
 No. of particles: CCD-B = 11495402, CCD-Z = 79019
 Velocity adaption: no
 Fitting: no

Material:

ASTM(+)	No(-)	retained [%]	passing [%]	SPHT3	Symm3	b/l3	PDN
> #16		11.8	100.0	0.833	0.894	0.740	749
#20	#16	19.7	88.2	0.838	0.900	0.717	3216
#30	#20	22.7	68.5	0.853	0.903	0.725	9892
#40	#30	15.6	45.8	0.868	0.905	0.733	19066
#50	#40	9.3	30.2	0.883	0.905	0.744	32871
#60	#50	3.3	20.9	0.892	0.904	0.752	26930
#70	#60	2.4	17.6	0.901	0.904	0.758	33168
#140	#70	7.3	15.2	0.892	0.900	0.755	397870
PAN	#140	7.9	7.9	0.890	0.925	0.764	12811512

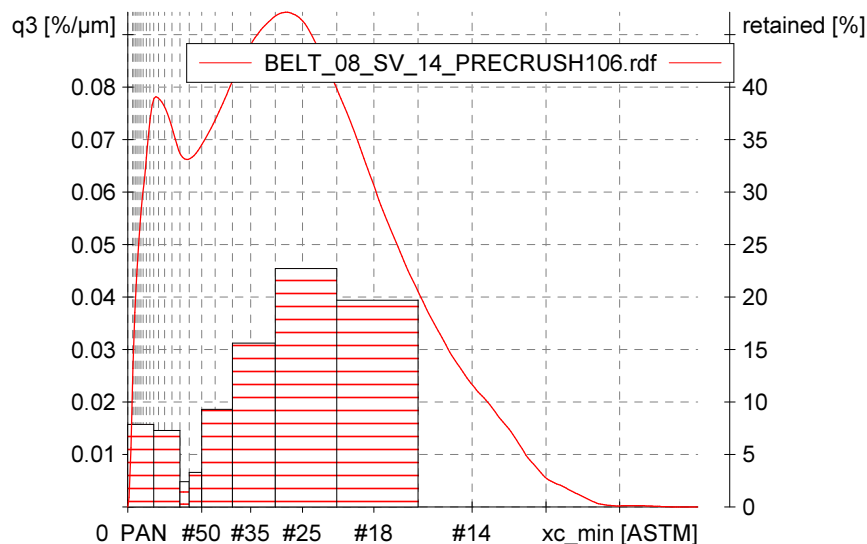

Characteristics

Q3 [%]	x [μm]
10.0	132.1
50.0	644.6
90.0	1228.8
SPAN3 =	1.701
U3 =	5.672
Mv3(x) =	670.6 μm
Sigma3(x) =	399.8 μm

Mean value SPHT3 = 0.857
 Mean value Symm3 = 0.903
 Mean value b/l3 = 0.722
 Mean value RDNS_C3 = 0.486
 Mean value SPHT_K3 = 0.646

User