


BELT_12_SV_14_CRUSH5K

Company:
 User:
 Result file: C:\CamsizerXT\CAMDAT\BELT_12_SV_14_CRUSH5K\BELT_12_SV_14_CRUSH5K140.rdf
 Task file: C:\CamsizerXT\CAMSYS\BELT_12_SV_14_CRUSH5K.afg
 Time: 6/15/2015 , 15:45 , duration 18 min 4 s at 0.5 % covered area, image rate 1:1 , with X-Fall, gap width = 7.0 mm

Particle model: xc_min
 No. of particles: CCD-B = 42047364 , CCD-Z = 413596
 Velocity adaption: no
 Fitting: no

Material:

ASTM(+)	No(-)	retained [%]	passing [%]	SPHT3	Symm3	b/l3	PDN
> #16		0.0	100.0				0
#20	#16	0.0	100.0	0.851	0.911	0.676	2
#30	#20	0.0	100.0	0.660	0.795	0.567	2
#40	#30	0.5	100.0	0.848	0.863	0.784	1232
#50	#40	22.3	99.5	0.909	0.902	0.779	141186
#60	#50	37.3	77.2	0.922	0.913	0.762	408640
#70	#60	22.6	39.9	0.920	0.914	0.734	373174
#140	#70	13.5	17.3	0.895	0.903	0.702	616255
PAN	#140	3.8	3.8	0.837	0.898	0.676	70248274

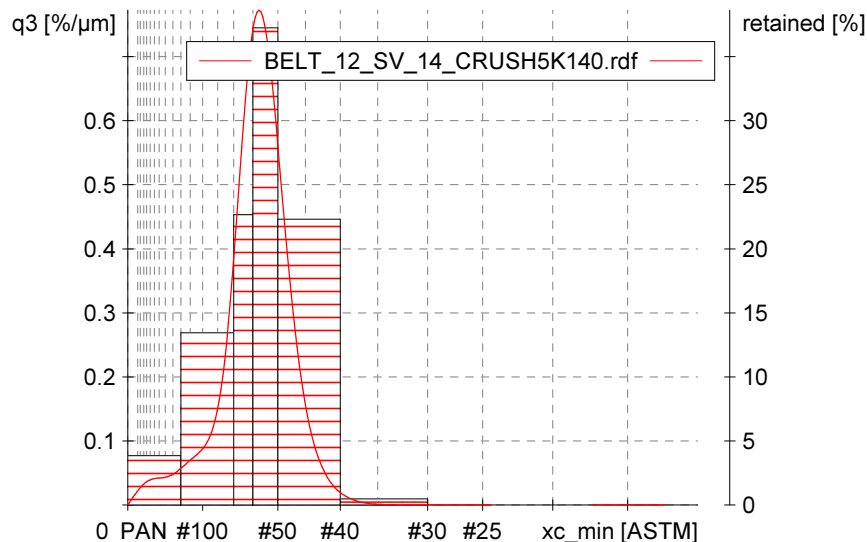

Characteristics

Q3 [%]	x [μm]
10.0	179.7
50.0	262.4
90.0	330.2
SPAN3 =	0.573
U3 =	1.529
Mv3(x) =	257.2 μm
Sigma3(x) =	67.2 μm

Mean value SPHT3 = 0.906
 Mean value Symm3 = 0.907
 Mean value b/l3 = 0.735
 Mean value RDNS_C3 = 0.606
 Mean value SPHT_K3 = 0.676

User