


BELT_13_5kcrush

Company:
 User:
 Result file: C:\CamsizerXT\CAMDAT\BELT_13_5kcrush\BELT_13_5kcrush050.rdf
 Task file: C:\CamsizerXT\CAMSYS\BELT_13_5kcrush.afg
 Time: 3/5/2015 , 14:09 , duration 14 min 30 s at 0.5 % covered area, image rate 1:1 , with X-Fall, gap width = 7.0 mm

Particle model: xc_min
 No. of particles: CCD-B = 31681892 , CCD-Z = 204425
 Velocity adaption: no
 Fitting: no

Material:

ASTM(+)	No(-)	retained [%]	passing [%]	SPHT3	Symm3	b/l3	PDN
> #16		0.0	100.0				0
#20	#16	0.0	100.0	0.419	0.657	0.688	1
#30	#20	4.7	100.0	0.886	0.899	0.791	8511
#40	#30	38.9	95.3	0.900	0.907	0.765	150404
#50	#40	45.1	56.4	0.903	0.908	0.744	418596
#60	#50	5.3	11.3	0.883	0.900	0.688	100370
#70	#60	1.8	6.0	0.875	0.893	0.687	56137
#140	#70	2.7	4.2	0.856	0.886	0.672	314161
PAN	#140	1.5	1.5	0.778	0.879	0.615	85489622

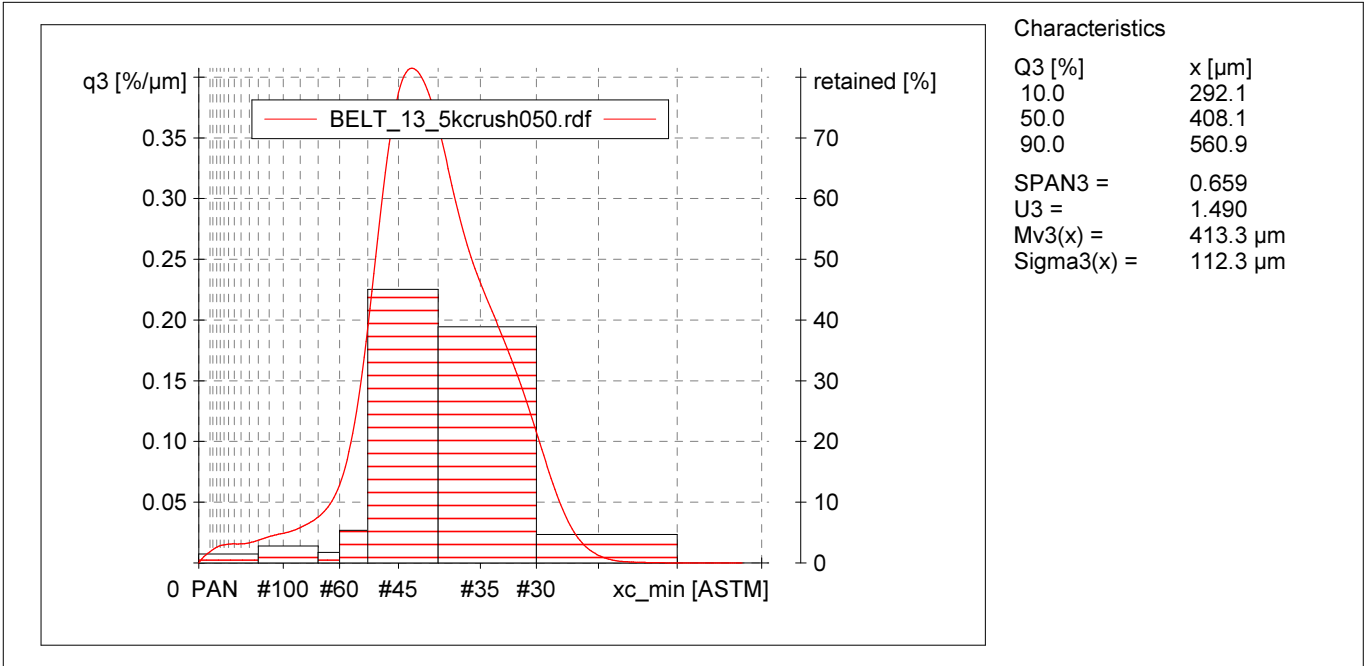

Mean value SPHT3 = 0.891
 Mean value Symm3 = 0.905
 Mean value b/l3 = 0.733
 Mean value RDNS_C3 = 0.568
 Mean value SPHT_K3 = 0.674

 User