


BELT_13_6kcrush

Company:
 User:
 Result file: C:\CamsizerXT\CAMDAT\BELT_13_6kcrush\BELT_13_6kcrush049.rdf
 Task file: C:\CamsizerXT\CAMSYS\BELT_13_6kcrush.afg
 Time: 3/5/2015 , 12:48 , duration 17 min 36 s at 0.5 % covered area, image rate 1:1 , with X-Fall, gap width = 7.0 mm

Particle model: xc_min
 No. of particles: CCD-B = 69146406 , CCD-Z = 573793
 Velocity adaption: no
 Fitting: no

Material:

ASTM(+)	No(-)	retained [%]	passing [%]	SPHT3	Symm3	b/l3	PDN
> #16		0.0	100.0				0
#20	#16	0.0	100.0				0
#30	#20	2.7	100.0	0.889	0.902	0.794	4902
#40	#30	28.3	97.3	0.900	0.907	0.769	111199
#50	#40	50.1	69.0	0.905	0.908	0.750	463095
#60	#50	7.4	18.9	0.885	0.899	0.701	140046
#70	#60	2.9	11.5	0.879	0.892	0.699	93810
#140	#70	5.4	8.6	0.860	0.887	0.674	595707
PAN	#140	3.2	3.2	0.822	0.893	0.649	157105470

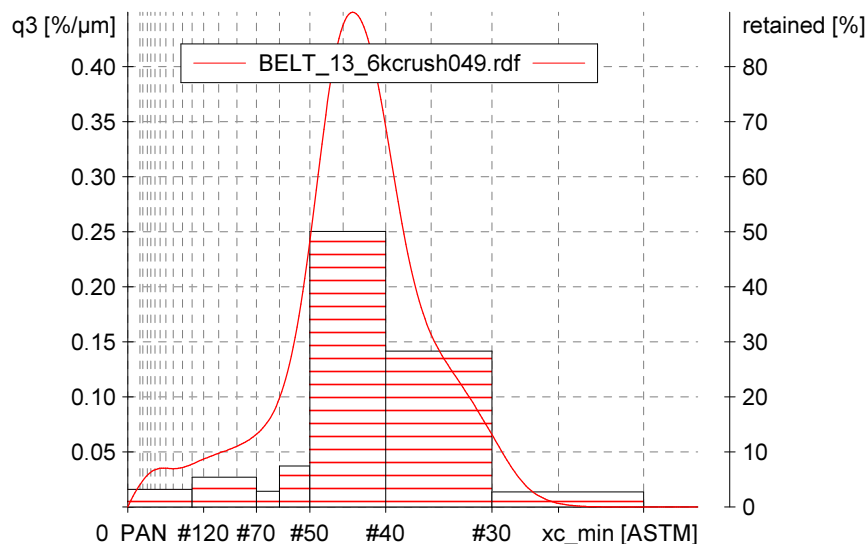

Characteristics

Q3 [%]	x [μm]
10.0	232.1
50.0	379.3
90.0	526.5
SPAN3 =	0.776
U3 =	1.731
Mv3(x) =	377.2 μm
Sigma3(x) =	117.8 μm

Mean value SPHT3 = 0.891
 Mean value Symm3 = 0.904
 Mean value b/l3 = 0.732
 Mean value RDNS_C3 = 0.564
 Mean value SPHT_K3 = 0.670

User