


C81_1_5KCRUSH

Company:
 User:
 Result file: C:\CamsizerXT\CAMDAT\C81_1_5KCRUSH\C81_1_5KCRUSH135.rdf
 Task file: C:\CamsizerXT\CAMSYS\C81_1_5KCRUSH.afg
 Time: 12/4/2015 , 14:54 , duration 17 min 8 s at 0.5 % covered area, image rate 1:1 , with X-Fall, gap width = 7.0 mm

Particle model: xc_min
 No. of particles: CCD-B = 28662134 , CCD-Z = 377241
 Velocity adaption: no
 Fitting: no

Material:

ASTM(+)	No(-)	retained [%]	passing [%]	SPHT3	Symm3	b/l3	PDN
> #16		0.0	100.0				0
#20	#16	0.0	100.0				0
#30	#20	0.1	100.0	0.711	0.812	0.712	84
#40	#30	5.3	99.9	0.873	0.880	0.778	11701
#50	#40	58.1	94.6	0.913	0.909	0.764	278686
#60	#50	22.4	36.5	0.911	0.911	0.730	199257
#70	#60	6.9	14.1	0.901	0.905	0.709	96993
#140	#70	5.1	7.2	0.882	0.896	0.692	226231
PAN	#140	2.1	2.1	0.859	0.905	0.697	51569950

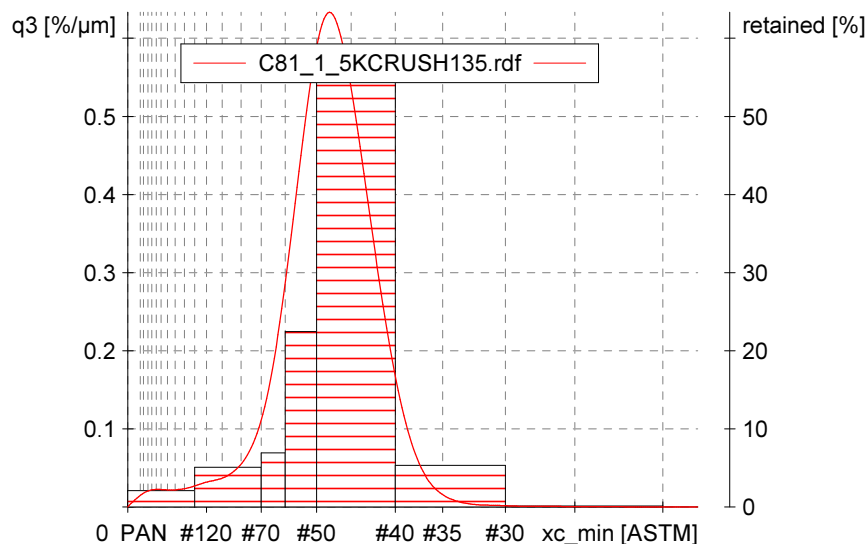

Characteristics

Q3 [%]	x [μm]
10.0	232.3
50.0	321.3
90.0	403.6
SPAN3 = 0.533	
U3 = 1.451	
Mv3(x) = 317.0 μm	
Sigma3(x) = 76.8 μm	

Mean value SPHT3 = 0.901
 Mean value Symm3 = 0.905
 Mean value b/l3 = 0.735
 Mean value RDNS_C3 = 0.615
 Mean value SPHT_K3 = 0.677

User