


C82_03_6KCRUSH

Company:
 User:
 Result file: C:\CamsizerXT\CAMDAT\C82_03_6KCRUSH\C82_03_6KCRUSH100.rdf
 Task file: C:\CamsizerXT\CAMSYS\C82_03_6KCRUSH.afg
 Time: 11/5/2015 , 15:45 , duration 28 min 37 s at 0.5 % covered area, image rate 1:1 , with X-Fall, gap width = 7.0 mm

Particle model: xc_min
 No. of particles: CCD-B = 34958217 , CCD-Z = 583309
 Velocity adaption: no
 Fitting: no

Material:

ASTM(+)	No(-)	retained [%]	passing [%]	SPHT3	Symm3	b/l3	PDN
> #16		0.0	100.0				0
#20	#16	0.0	100.0				0
#30	#20	0.0	100.0				0
#40	#30	0.0	100.0				0
#50	#40	0.0	100.0	0.707	0.759	0.739	145
#60	#50	1.3	100.0	0.887	0.878	0.778	9804
#70	#60	11.3	98.7	0.919	0.900	0.772	129912
#140	#70	78.6	87.4	0.913	0.906	0.741	2859113
PAN	#140	8.8	8.8	0.883	0.916	0.706	66521281

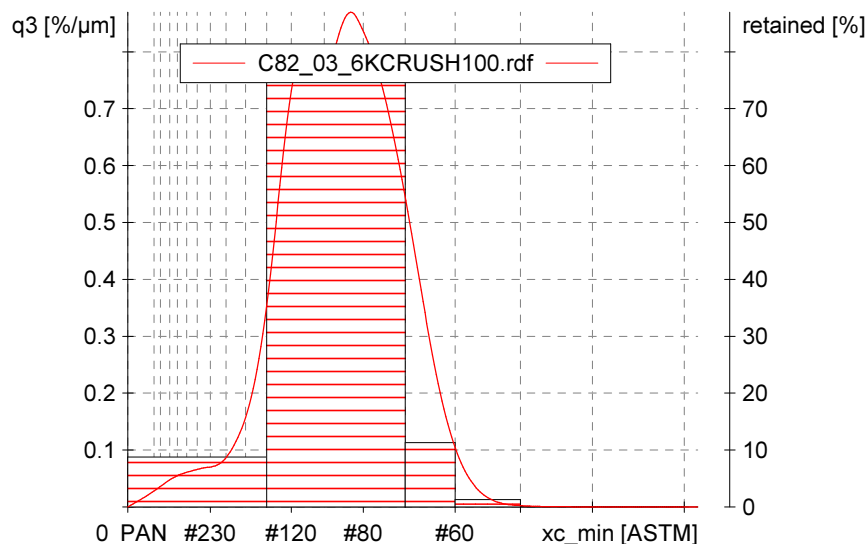

Characteristics

Q3 [%]	x [μm]
10.0	109.3
50.0	163.6
90.0	217.1
SPAN3 = 0.659	
U3 = 1.599	
Mv3(x) = 161.7 μm	
Sigma3(x) = 44.3 μm	

Mean value SPHT3 = 0.904
 Mean value Symm3 = 0.905
 Mean value b/l3 = 0.726
 Mean value RDNS_C3 = 0.648
 Mean value SPHT_K3 = 0.649

User