


DILL_01_SV_14_CRUSH5K

Company:
 User:
 Result file: C:\CamsizerXT\CAMDAT\DILL_01_SV_14_CRUSH5K\DILL_01_SV_14_CRUSH5K028.rdf
 Task file: C:\CamsizerXT\CAMSYS\DILL_01_SV_14_CRUSH5K.afg
 Time: 2/6/2015, 8:59, duration 25 min 0 s at 0.5 % covered area, image rate 1:1, with X-Fall, gap width = 7.0 mm

Particle model: xc_min
 No. of particles: CCD-B = 106953469, CCD-Z = 881393
 Velocity adaption: no
 Fitting: no

Material:

ASTM(+)	No(-)	retained [%]	passing [%]	SPHT3	Symm3	b/l3	PDN
> #16		0.0	100.0				0
#20	#16	0.0	100.0				0
#30	#20	0.0	100.0				0
#40	#30	0.0	100.0				0
#50	#40	0.0	100.0	0.669	0.752	0.729	159
#60	#50	0.7	100.0	0.887	0.878	0.784	10585
#70	#60	6.7	99.3	0.920	0.901	0.780	159969
#140	#70	79.6	92.6	0.913	0.905	0.747	6781975
PAN	#140	13.0	13.0	0.866	0.906	0.689	197332358

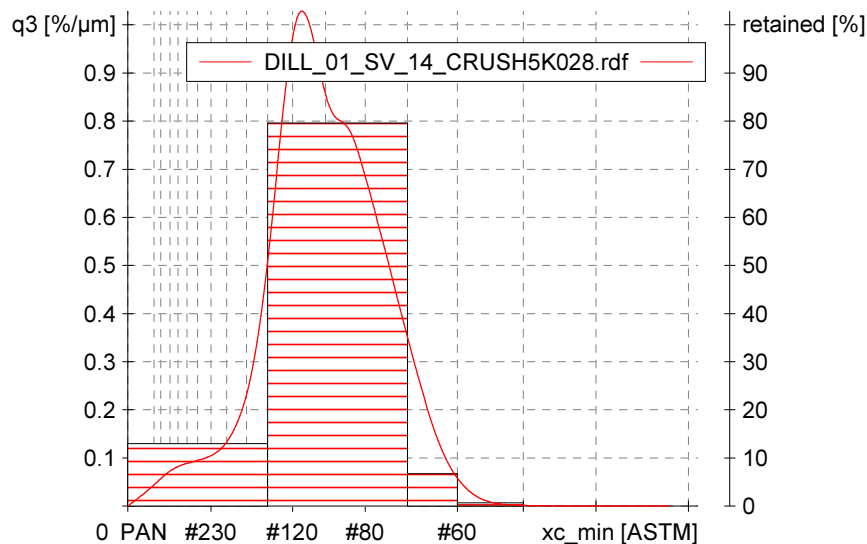

Characteristics

Q3 [%]	x [μm]
10.0	98.5
50.0	147.1
90.0	205.3
SPAN3 =	0.727
U3 =	1.620
Mv3(x) =	148.9 μm
Sigma3(x) =	43.9 μm

Mean value SPHT3 = 0.901
 Mean value Symm3 = 0.903
 Mean value b/l3 = 0.727
 Mean value RDNS_C3 = 0.578
 Mean value SPHT_K3 = 0.654

User