


DILL_02_SV_14_CRUSH6k

Company:
 User:
 Result file: C:\CamsizerXT\CAMDAT\DILL_02_SV_14_CRUSH6k\DILL_02_SV_14_CRUSH6k021.rdf
 Task file: C:\CamsizerXT\CAMSYS\DILL_02_SV_14_CRUSH6k.afg
 Time: 2/9/2015 , 14:26 , duration 30 min 31 s at 0.5 % covered area, image rate 1:1 , with X-Fall, gap width = 7.0 mm

Particle model: xc_min
 No. of particles: CCD-B = 91760387 , CCD-Z = 928828
 Velocity adaption: no
 Fitting: no

Material:

ASTM(+)	No(-)	retained [%]	passing [%]	SPHT3	Symm3	b/l3	PDN
> #16		0.0	100.0				0
#20	#16	0.0	100.0				0
#30	#20	0.0	100.0	0.514	0.721	0.766	2
#40	#30	1.6	100.0	0.903	0.896	0.805	7173
#50	#40	34.3	98.4	0.921	0.910	0.778	351981
#60	#50	30.7	64.1	0.921	0.911	0.757	584057
#70	#60	16.8	33.4	0.917	0.910	0.734	486161
#140	#70	12.2	16.6	0.893	0.900	0.702	1043630
PAN	#140	4.4	4.4	0.857	0.904	0.689	174043598

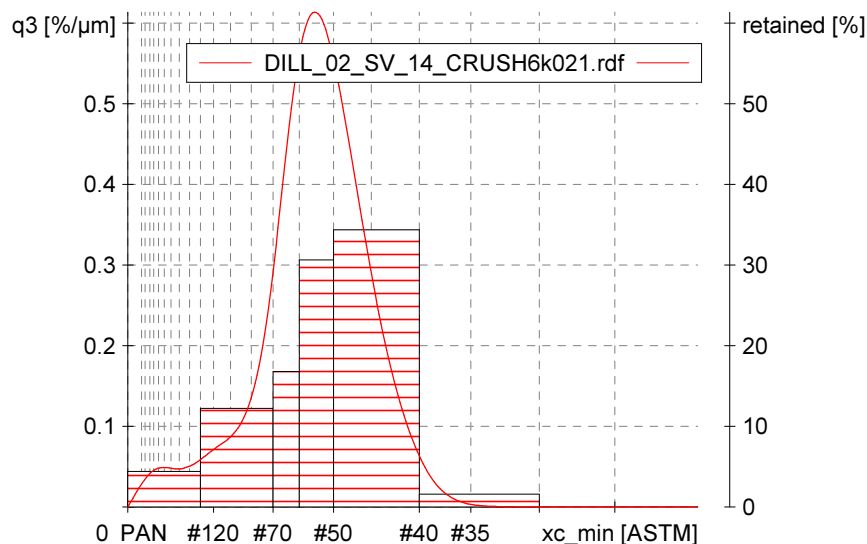

Characteristics

Q3 [%]	x [μm]
10.0	174.7
50.0	276.7
90.0	364.4
SPAN3 =	0.685
U3 =	1.677
Mv3(x) =	271.9 μm
Sigma3(x) =	78.8 μm

Mean value SPHT3 = 0.909
 Mean value Symm3 = 0.908
 Mean value b/l3 = 0.739
 Mean value RDNS_C3 = 0.661
 Mean value SPHT_K3 = 0.682

User