


DILL_08_SV_14_CRUSH6K

Company:
 User:
 Result file: C:\CamsizerXT\CAMDAT\DILL_08_SV_14_CRUSH6K\DILL_08_SV_14_CRUSH6K048.rdf
 Task file: C:\CamsizerXT\CAMSYS\DILL_08_SV_14_CRUSH6K.afg
 Time: 2/23/2015, 15:17, duration 28 min 5 s at 0.5 % covered area, image rate 1:1, with X-Fall, gap width = 7.0 mm

Particle model: xc_min
 No. of particles: CCD-B = 104567492, CCD-Z = 916655
 Velocity adaption: no
 Fitting: no

Material:

ASTM(+)	No(-)	retained [%]	passing [%]	SPHT3	Symm3	b/l3	PDN
> #16		0.0	100.0	0.555	0.793	0.537	1
#20	#16	0.0	100.0				0
#30	#20	0.0	100.0	0.531	0.812	0.440	2
#40	#30	0.0	100.0	0.696	0.852	0.509	17
#50	#40	0.1	100.0	0.694	0.783	0.696	443
#60	#50	0.4	99.9	0.817	0.836	0.756	6506
#70	#60	3.7	99.5	0.897	0.885	0.777	95974
#140	#70	85.8	95.8	0.912	0.905	0.750	7234945
PAN	#140	10.0	10.0	0.872	0.909	0.704	158161507

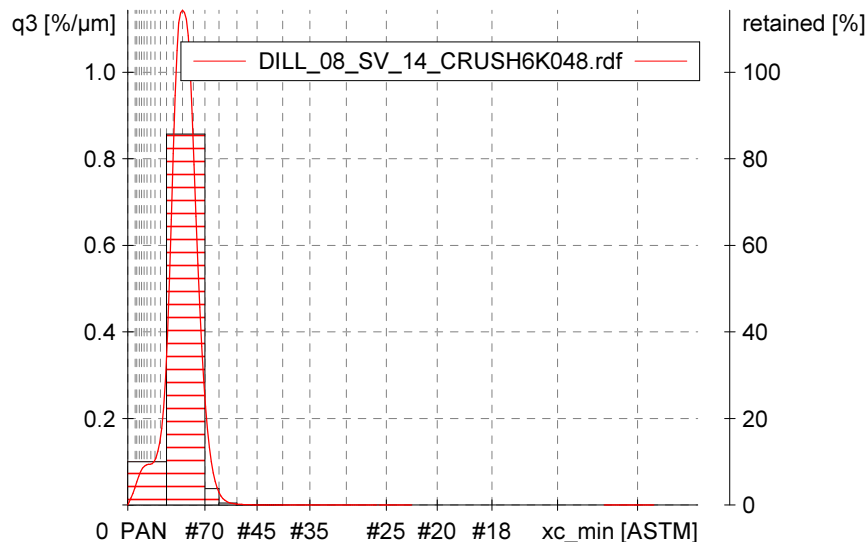

Characteristics

Q3 [%]	x [μm]
10.0	105.9
50.0	152.1
90.0	195.4
SPAN3 =	0.589
U3 =	1.520
Mv3(x) =	150.3 μm
Sigma3(x) =	42.0 μm

Mean value SPHT3 = 0.901
 Mean value Symm3 = 0.902
 Mean value b/l3 = 0.731
 Mean value RDNS_C3 = 0.621
 Mean value SPHT_K3 = 0.665

User