


ENN_01_SV_14_PRECRUSH

Company:
 User:
 Result file: C:\CamsizerXT\CAMDAT\ENN_01_SV_14_PRECRUSH\ENN_01_SV_14_PRECRUSH031.rdf
 Task file: C:\CamsizerXT\CAMSYS\ENN_01_SV_14_PRECRUSH.afg
 Time: 5/15/2015 , 12:12 , duration 11 min 37 s at 0.5 % covered area, image rate 1:1 , with X-Fall, gap width = 7.0 mm

Particle model: xc_min
 No. of particles: CCD-B = 8820563 , CCD-Z = 171472
 Velocity adaption: no
 Fitting: no

Material:

ASTM(+)	No(-)	retained [%]	passing [%]	SPHT3	Symm3	b/l3	PDN
> #16		11.1	100.0	0.728	0.886	0.643	291
#20	#16	8.3	88.9	0.753	0.880	0.668	807
#30	#20	8.5	80.6	0.774	0.879	0.688	2347
#40	#30	7.4	72.1	0.797	0.875	0.697	5853
#50	#40	7.2	64.7	0.825	0.874	0.711	16913
#60	#50	4.2	57.5	0.846	0.872	0.717	21195
#70	#60	4.8	53.3	0.869	0.877	0.728	42009
#140	#70	40.1	48.5	0.903	0.904	0.741	1354095
PAN	#140	8.4	8.4	0.893	0.926	0.734	19866014

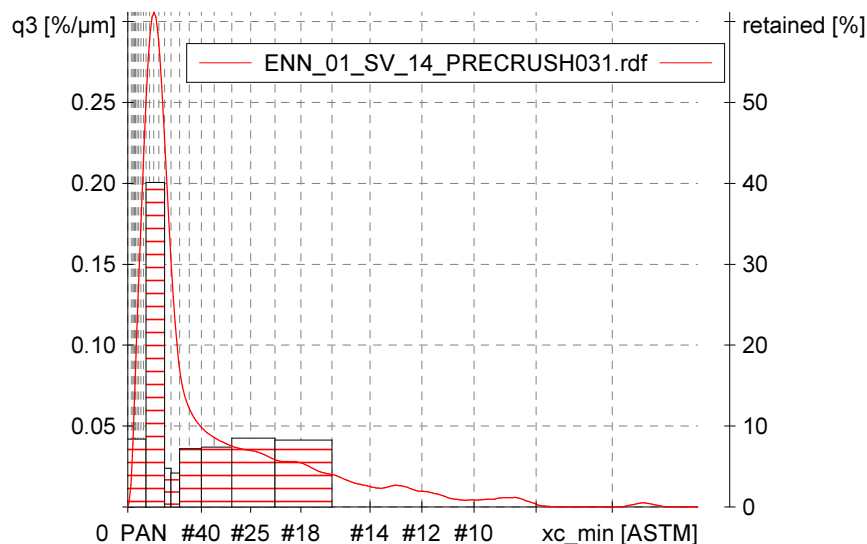

Characteristics

Q3 [%]	x [μm]
10.0	111.2
50.0	221.6
90.0	1229.2
SPAN3 =	5.046
U3 =	3.037
Mv3(x) =	482.8 μm
Sigma3(x) =	511.5 μm

Mean value SPHT3 = 0.836
 Mean value Symm3 = 0.892
 Mean value b/l3 = 0.698
 Mean value RDNS_C3 = 0.395
 Mean value SPHT_K3 = 0.598

User