


ENN_05_SV_14_PRECRUSH

Company:
 User:
 Result file: C:\CamsizerXT\CAMDAT\ENN_05_SV_14_PRECRUSH\ENN_05_SV_14_PRECRUSH111.rdf
 Task file: C:\CamsizerXT\CAMSYS\ENN_05_SV_14_PRECRUSH.afg
 Time: 6/11/2015, 13:41, duration 9 min 37 s at 0.5 % covered area, image rate 1:1, with X-Fall, gap width = 7.0 mm

Particle model: xc_min
 No. of particles: CCD-B = 1431903, CCD-Z = 29465
 Velocity adaption: no
 Fitting: no

Material:

ASTM(+)	No(-)	retained [%]	passing [%]	SPHT3	Symm3	b/l3	PDN
> #16		21.0	100.0	0.725	0.875	0.677	562
#20	#16	16.3	79.0	0.742	0.874	0.665	1478
#30	#20	15.6	62.7	0.759	0.870	0.673	3812
#40	#30	11.2	47.1	0.782	0.867	0.683	7825
#50	#40	8.9	35.9	0.816	0.868	0.694	18094
#60	#50	4.6	27.0	0.852	0.875	0.713	21414
#70	#60	4.6	22.4	0.879	0.884	0.724	35687
#140	#70	16.9	17.8	0.894	0.901	0.729	438153
PAN	#140	0.9	0.9	0.860	0.918	0.676	5850377

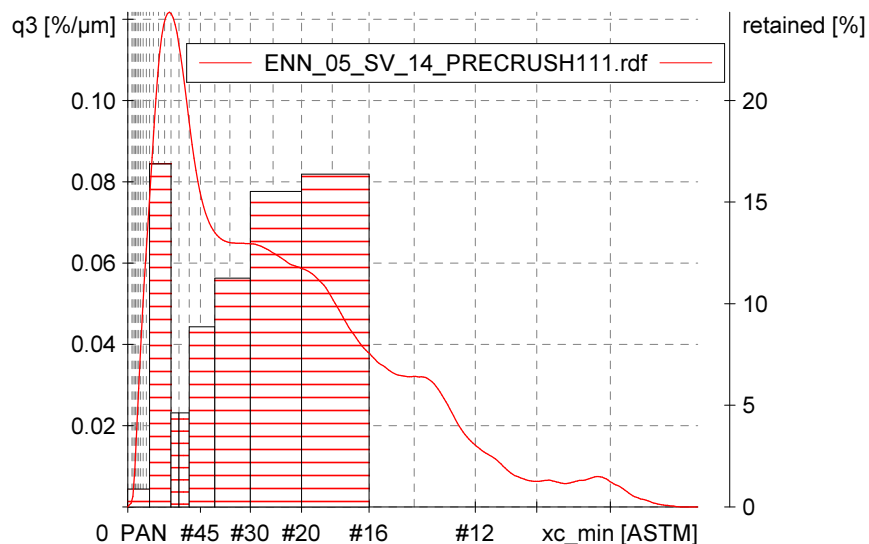

Characteristics

Q3 [%]	x [μm]
10.0	166.5
50.0	643.7
90.0	1505.0
SPAN3 = 2.079	
U3 = 4.842	
Mv3(x) = 750.1 μm	
Sigma3(x) = 537.6 μm	

Mean value SPHT3 = 0.785
 Mean value Symm3 = 0.877
 Mean value b/l3 = 0.675
 Mean value RDNS_C3 = 0.277
 Mean value SPHT_K3 = 0.555

User