


ENN_14_SV_14_PRECRUSH

Company:
 User:
 Result file: C:\CamsizerXT\CAMDAT\ENN_14_SV_14_PRECRUSH\ENN_14_SV_14_PRECRUSH122.rdf
 Task file: C:\CamsizerXT\CAMSYS\ENN_14_SV_14_PRECRUSH.afg
 Time: 6/12/2015, 11:11, duration 10 min 39 s at 0.5 % covered area, image rate 1:1, with X-Fall, gap width = 7.0 mm

Particle model: xc_min
 No. of particles: CCD-B = 10072628, CCD-Z = 99756
 Velocity adaption: no
 Fitting: no

Material:

ASTM(+)	No(-)	retained [%]	passing [%]	SPHT3	Symm3	b/l3	PDN
> #16		11.1	100.0	0.727	0.871	0.669	662
#20	#16	11.2	88.9	0.742	0.871	0.665	1893
#30	#20	10.3	77.7	0.760	0.868	0.670	4857
#40	#30	8.8	67.4	0.789	0.866	0.687	12126
#50	#40	11.5	58.6	0.841	0.874	0.714	48364
#60	#50	8.5	47.1	0.872	0.883	0.724	76006
#70	#60	9.5	38.6	0.892	0.892	0.731	142450
#140	#70	27.5	29.1	0.898	0.901	0.722	1191934
PAN	#140	1.6	1.6	0.849	0.909	0.663	30962009

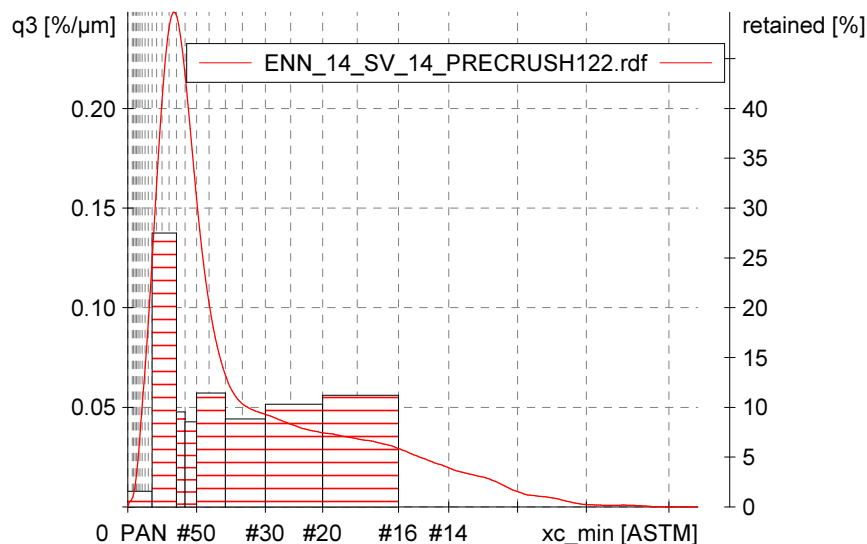

Characteristics

Q3 [%]	x [μm]
10.0	154.1
50.0	322.4
90.0	1217.1
SPAN3 = 3.298	
U3 = 2.922	
Mv3(x) = 526.6 μm	
Sigma3(x) = 433.7 μm	

Mean value SPHT3 = 0.821
 Mean value Symm3 = 0.881
 Mean value b/l3 = 0.684
 Mean value RDNS_C3 = 0.309
 Mean value SPHT_K3 = 0.572

User