


GFS_06_CRUSH6K

Company:
 User:
 Result file: C:\CamsizerXT\CAMDAT\GFS_06_CRUSH6K\GFS_06_CRUSH6K058.rdf
 Task file: C:\CamsizerXT\CAMSYS\GFS_06_CRUSH6K.afg
 Time: 8/12/2015, 11:11, duration 28 min 55 s at 0.5 % covered area, image rate 1:1, with X-Fall, gap width = 7.0 mm

Particle model: xc_min
 No. of particles: CCD-B = 47982983, CCD-Z = 418937
 Velocity adaption: no
 Fitting: no

Material:

ASTM(+)	No(-)	retained [%]	passing [%]	SPHT3	Symm3	b/l3	PDN
> #16		0.0	100.0				0
#20	#16	0.0	100.0				0
#30	#20	0.0	100.0	0.617	0.805	0.799	1
#40	#30	0.6	100.0	0.859	0.877	0.780	944
#50	#40	15.0	99.4	0.894	0.895	0.772	54144
#60	#50	27.6	84.4	0.912	0.905	0.768	186509
#70	#60	24.8	56.8	0.914	0.908	0.745	251866
#140	#70	22.0	32.0	0.894	0.902	0.712	638116
PAN	#140	10.0	10.0	0.851	0.900	0.705	60553008

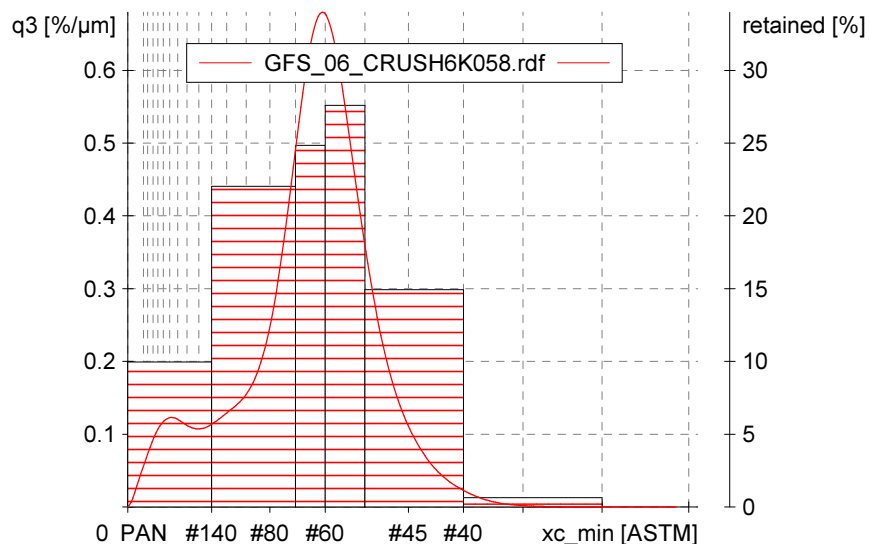

Characteristics

Q3 [%]	x [μm]
10.0	106.4
50.0	240.7
90.0	319.6
SPAN3 =	0.886
U3 =	2.392
Mv3(x) =	230.0 μm
Sigma3(x) =	81.1 μm

Mean value SPHT3 = 0.895
 Mean value Symm3 = 0.902
 Mean value b/l3 = 0.731
 Mean value RDNS_C3 = 0.545
 Mean value SPHT_K3 = 0.669

User