


WSS_01_SV_14_CRUSH6K

Company:
 User:
 Result file: C:\CamsizerXT\CAMDAT\WSS_01_SV_14_CRUSH6K\WSS_01_SV_14_CRUSH6K043.rdf
 Task file: C:\CamsizerXT\CAMSYS\WSS_01_SV_14_CRUSH6K.afg
 Time: 8/4/2015 , 13:48 , duration 22 min 35 s at 0.5 % covered area, image rate 1:1 , with X-Fall, gap width = 7.0 mm

Particle model: xc_min
 No. of particles: CCD-B = 30807121 , CCD-Z = 318216
 Velocity adaption: no
 Fitting: no

Material:

ASTM(+)	No(-)	retained [%]	passing [%]	SPHT3	Symm3	b/l3	PDN
> #16		0.0	100.0				0
#20	#16	0.0	100.0	0.872	0.888	0.768	1
#30	#20	2.7	100.0	0.888	0.899	0.795	1076
#40	#30	30.2	97.3	0.899	0.907	0.767	25014
#50	#40	39.1	67.1	0.903	0.907	0.750	80780
#60	#50	8.7	28.0	0.890	0.899	0.716	37098
#70	#60	4.3	19.3	0.883	0.893	0.708	31203
#140	#70	8.7	15.0	0.861	0.886	0.676	211646
PAN	#140	6.3	6.3	0.827	0.892	0.651	52081529

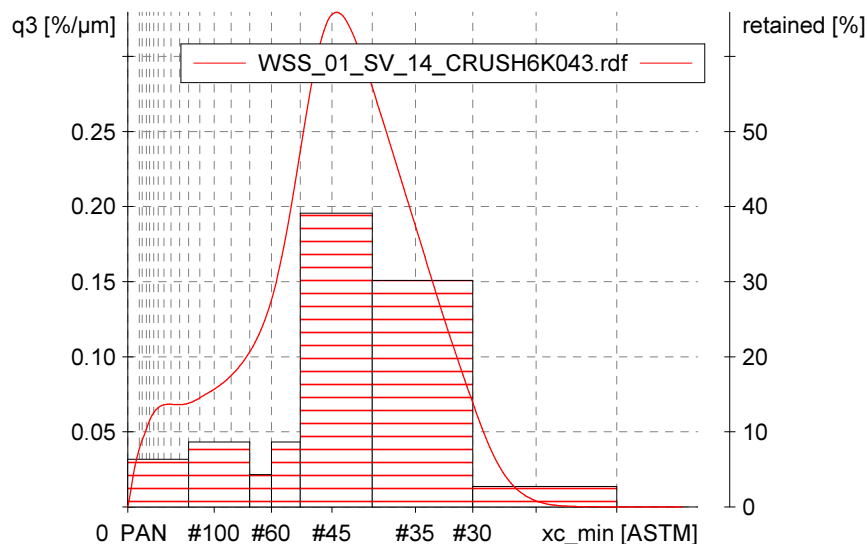

Characteristics

Q3 [%]	x [μm]
10.0	155.3
50.0	370.0
90.0	531.7
SPAN3 = 1.017	
U3 = 2.581	
Mv3(x) = 360.3 μm	
Sigma3(x) = 138.8 μm	

Mean value SPHT3 = 0.886
 Mean value Symm3 = 0.902
 Mean value b/l3 = 0.726
 Mean value RDNS_C3 = 0.557
 Mean value SPHT_K3 = 0.658

User